

THE EFFECT OF NIOBIUM CONTENT ON THE CURIE TEMPERATURE AND MICROSTRUCTURE OF THE $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_{16}\text{B}_6\text{Nb}_x$ Alloys

L. P. Barbosa, H. Takiishi, R. N. Faria*
Rodrigues, D.; Janasi, S. R., Stranguetti, A. **
Instituto de Pesquisas Energéticas e Nucleares, IPEN-CNEN*
Instituto de Pesquisas Tecnológicas, IPT**
São Paulo- Brazil
luzinete@ipen.br

Abstract: *This study reports the results of investigations carried out to determine the Curie temperature (T_c) of various homogenized praseodymium-based alloys represented by the formula: $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_{16}\text{B}_6\text{Nb}_x$ (where $x = 0, 0.01, 0.05, 0.1, 0.15, 0.50$). The influence of niobium content on the microstructure of these alloys has investigated. The Curie temperature decreased about 3 °C for $x = 0.5$ at. %. It has been observed a remarkable grain refinement on the microstructure of the $\text{Pr}_{14}\text{Fe}_{79.8}\text{Co}_{16}\text{B}_6\text{Nb}_{0.1}$ alloy when compared to the niobium-free alloy ($x = 0$ at. %).*

Keywords: *Pr-based alloys, Curie temperature, magnetic materials*

INTRODUCTION

The $\text{R}_2\text{Fe}_{14}\text{B}$ compounds (R =Yttrium or a rare earth) have been studied extensively since their discovery in 1983^[1]. High energy permanent magnets have been produced with these outstanding materials. Magnets with high energy products have been produced mainly with the Nd/PrFeB system. A major drawback of the this system is their rather low Curie temperature ($\sim 300^\circ\text{C}$)^[2]. Improvement of these magnets has been achieved in the 2:14:1 compounds by the substitution of cobalt in the magnetic alloys^[3, 4]. The replacement of Fe for Co ($\text{Pr}_2\text{Fe}_{14-x}\text{Co}_x\text{B}$) increased the Curie temperature^[4]. The $\text{Pr}_2\text{Fe}_{13}\text{Co}_1\text{B}$ compound has a higher T_c than $\text{Pr}_2\text{Fe}_{14}\text{B}$ ^[1, 5] and it has been shown that the Co atoms substitute preferentially on Fe sites, involving negative exchange interactions^[5]. It has been reported that the Curie temperature of $\text{Nd}_2\text{Fe}_{14}\text{B}$ increases linearly with the Co content at about 11°C per at.%^[6]. Recently, it has been shown for $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_x\text{B}_6\text{Nb}_{0.1}$ alloys that T_c also increase linearly with the Co content, although at rate slightly inferior to that reported

for Nd-based materials ($\sim 10.2 \pm 0.3^\circ\text{C}/\text{at.}\%$)^[7,8]. In the $\text{PrCo}_{5-x}\text{Ga}_x$ system, the Curie temperature decrease with gallium addition^[9]. Similarly, the substitution of Fe for Nb also decreases the Curie temperature^[1]. The present work was undertaken in order to investigate, in a systematic manner, the progressive effect of Nb substitution for Fe in the Curie temperature and microstructure of some $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_{16}\text{B}_6\text{Nb}_x$ alloys, $x = 0, 0.01, 0.05, 0.1, 0.15, 0.5$.

EXPERIMENTAL

Commercially available alloys in the homogenized state were studied. The chemical analyses of the as-cast alloys are given in Table 1. Homogenization heat treatment was carried out by annealing of the as-cast alloys in vacuum at 1100°C for 20 h. A susceptibility analyzer was employed for thermomagnetic analysis (TMA) of the alloys in order to investigate their susceptibility versus temperature over the temperature range $50\text{--}500^\circ\text{C}$. A magnetic field of low amplitude (333 Hz) and heating rate of the alloys $1^\circ\text{C} / \text{min}$ were employed. $\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$, $\text{Pr}_{14}\text{Fe}_{64}\text{Co}_{16}\text{B}_6$ and $\text{Pr}_{14}\text{Fe}_{79.9}\text{Co}_{16}\text{B}_6\text{Nb}_{0.1}$ alloys were used as standard reference. The microstructures of the annealed alloys were observed using an optical microscope with Kerr effect facility and the chemical composition was observed with a SEM fitted with an EDX system.

RESULTS AND DISCUSSION

The variation in the Curie temperature of the annealed Pr-based alloys as a function of niobium content is shown in Fig 1. The Curie temperature decreases only 4°C for $x = 0.01, 0.05$ and 0.1 at.%. For higher Nb-contents, $x=0.15$ and 0.5 , a noticeable diminution in this property has been observed (9 and 11°C , respectively). Table 1 shows a summary of the Curie temperature for the various alloys investigated in this study. The substitution of 0.1 at.% Nb in the $\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$ alloy led to a decrease of 5°C in T_c . As expected, the substitution of 16 at.% Co in this alloy increased the Curie temperature in 157°C . This has been attributed to decrease of lattice parameters with the substitution (with changes of interatomic distance, which is crucial for exchange interactions)^[4]. The Curie temperature, which reflects the overall exchange, increases nearly 50°C per substituted Fe atom for Co (in region of low Co concentration)^[4]. The Curie temperature of the $\text{Pr}_2\text{Fe}_{14}\text{B}$ matrix phase, determined previously by differential thermal analysis (DTA), was $\sim 290^\circ\text{C}$ ^[10]. It has

been reported that compounds of the type $\text{Pr}_2\text{Fe}_{14-x}\text{Nb}_x\text{B}$ and $\text{Pr}_2\text{Fe}_{13-x}\text{Co}_1\text{Nb}_x\text{B}$ showed a decreased to Curie temperature in the composition range $x \leq 2$ ^[1]. Systems of the type $\text{Pr}_{1.9}\text{Dy}_{0.1}\text{Fe}_{13-x}\text{Nb}_x\text{Co}_1\text{B}$ also showed a decrease in this property^[1]. For a comparison with the present data these results are given in the table 2. The Curie temperature also decreases with increasing Nb content for these Dy-containing materials.

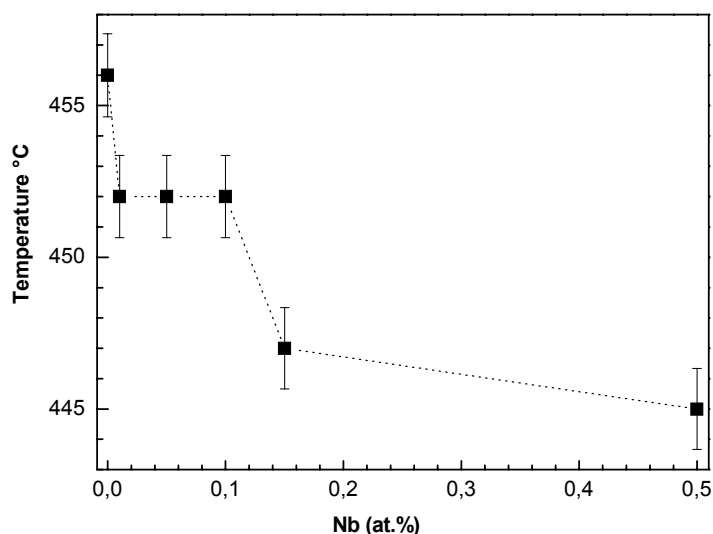


Figure 1 – Curie temperature versus niobium content for $\text{Pr}_{14}\text{Fe}_{79.9-x}\text{Co}_{16}\text{B}_6\text{Nb}_x$ magnetic alloys.

Table 1 - Curie temperature obtained in this study for magnetic alloys.

Alloys composition (at %)	T_c (°C)
$\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$	299
$\text{Pr}_{14}\text{Fe}_{79.9}\text{B}_6\text{Nb}_{0.1}$	294
$\text{Pr}_{14}\text{Fe}_{64}\text{Co}_{16}\text{B}_6$	456
$\text{Pr}_{14}\text{Fe}_{63.99}\text{Co}_{16}\text{B}_6\text{Nb}_{0.01}$	452
$\text{Pr}_{14}\text{Fe}_{63.95}\text{Co}_{16}\text{B}_6\text{Nb}_{0.05}$	452
$\text{Pr}_{14}\text{Fe}_{63.9}\text{Co}_{16}\text{B}_6\text{Nb}_{0.1}$	452
$\text{Pr}_{14}\text{Fe}_{63.85}\text{Co}_{16}\text{B}_6\text{Nb}_{0.15}$	447
$\text{Pr}_{14}\text{Fe}_{63.50}\text{Co}_{16}\text{B}_6\text{Nb}_{0.5}$	445

Table 2 - Curie temperature for similar systems^[1].

Alloys composition (at %)		T _c (°C)
Pr _{11.8} Fe _{82.3} B _{5.9}	(Pr ₂ Fe ₁₄ B)	293
Pr _{11.76} Fe _{81.91} Nb _{0.58} B _{5.75}	(Pr ₂ Fe _{13.9} Nb _{0.1} B)	290
Pr _{11.71} Fe _{81.21} Nb _{1.16} B _{5.92}	(Pr ₂ Fe _{13.8} Nb _{0.2} B)	287
Pr _{11.79} Fe _{76.79} Co _{5.53} B _{5.89}	(Pr ₂ Fe ₁₃ Co ₁ B)	355
Pr _{11.79} Fe _{75.91} Nb _{0.58} Co _{5.83} B _{5.89}	(Pr ₂ Fe _{12.9} Nb _{0.1} Co ₁ B)	352
Pr _{11.76} Fe _{75.31} Nb _{1.16} Co _{5.85} B _{5.92}	(Pr ₂ Fe _{12.8} Nb _{0.2} Co ₁ B)	348
Pr _{11.19} Dy _{0.6} Fe _{76.51} Co _{5.82} B _{5.88}	(Pr _{1.9} Dy _{0.1} Fe ₁₃ Co ₁ B)	359
Pr _{11.16} Dy _{0.58} Fe _{75.94} Nb _{0.58} Co _{5.84} B _{5.9}	(Pr _{1.9} Dy _{0.1} Fe _{12.9} Nb _{0.1} Co ₁ B)	357
Pr _{11.19} Dy _{0.58} Fe _{75.31} Nb _{1.16} Co _{5.85} B _{5.91}	(Pr _{1.9} Dy _{0.1} Fe _{12.8} Nb _{0.2} Co ₁ B)	354

Fig 2 shows the microstructure of the reference alloys. The Pr₁₄Fe₈₀B₆ alloy exhibits fine and elongated grains. Conversely, the Pr₁₄Fe_{79.9}B₆Nb_{0.1} alloy exhibits larger grains of the matrix phase. The microstructure of the Pr₁₄Fe₆₄Co₁₆B₆ alloy is composed of rounded grains. It is well known that in steels Nb acts as refinement of grains through carbide precipitation. A quantitative elemental analysis using EDX showed large amount of boride Pr_{1+ε}(FeCo)₄B₄ precipitated in the grain boundaries of the Pr₁₄Fe₈₀B₆ alloy, which could be the reason for the small grain size of this alloy.

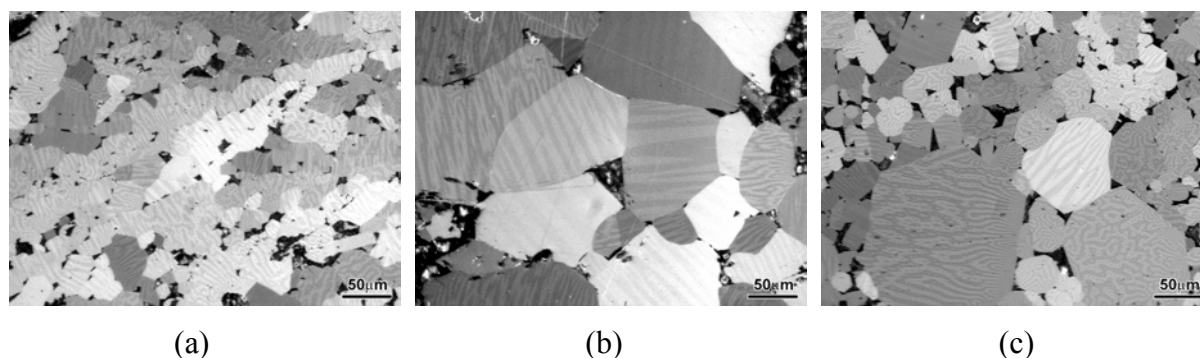


Figure 2 – Kerr effect image of the (a) Pr₁₄Fe₈₀B₆, (b) Pr₁₄Fe_{79.9}B₆Nb_{0.1} and (c) Pr₁₄Fe₆₄Co₁₆B₆ alloys.

The figures 3 and 4 show the microstructures of Pr₁₄Fe_{63.99}Co₁₆B₆Nb_{0.01} and Pr₁₄Fe_{63.95}Co₁₆B₆Nb_{0.05} alloys, respectively. The microstructures of these alloys are very similar, which would be expected since the variation in Nb content also was very small. In both cases, it is noticeable the increase in the grain size in relation to the Nb-free alloy.

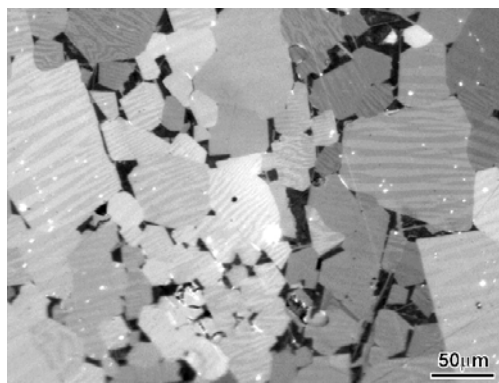


Figure 3 – Kerr effect image of the $\text{Pr}_{14}\text{Fe}_{63.99}\text{Co}_{16}\text{B}_6\text{Nb}_{0.01}$ alloy.

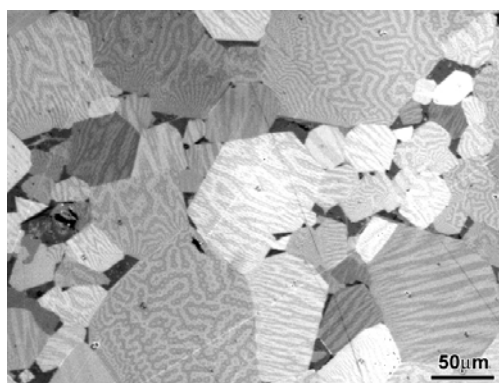


Figure 4 – Kerr effect image of the $\text{Pr}_{14}\text{Fe}_{63.95}\text{Co}_{16}\text{B}_6\text{Nb}_{0.05}$ alloy.

The substitution of 0.1 at.% Nb led to a significant change in the microstructure of the alloys, as shown in Fig. 5. The grain size is comparable to that observed in the $\text{Pr}_{14}\text{Fe}_{80}\text{B}_6$ alloy (Fig 2a). Chemical analyses showed the presence of a $\text{Pr}(\text{FeCo})_2$ in the grain boundaries. This Laves phase has been identified previously^[6, 11, 13].

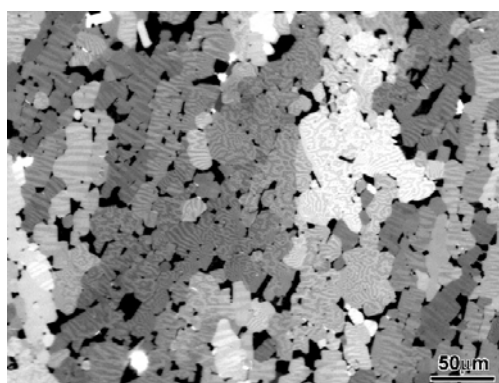


Figure 5 – Kerr effect image of the $\text{Pr}_{14}\text{Fe}_{63.9}\text{Co}_{16}\text{B}_6\text{Nb}_{0.1}$ alloy.

The increase in the Nb content to 0.15 at.% promoted some grain growth, as can be observed in the microstructure shown in Fig. 6. Chemical analyses in these alloys showed the presence of a Fe_2Nb phase^[7]. The alloy containing 0.5 at.% Nb also showed some change in the structure of the matrix phase grains, as shown in

Fig 7. Chemical analyses showed the presence of a Laves phase and a new FeNb phase. It is possible that higher Nb content lead the formation of precipitates in the grains boundaries, which could modify the structure of the grains.

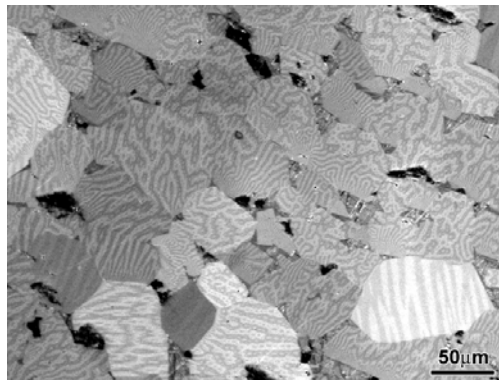


Figure 6 – Kerr effect image of the Pr₁₄Fe_{63.85}Co₁₆B₆Nb_{0.15} alloy.

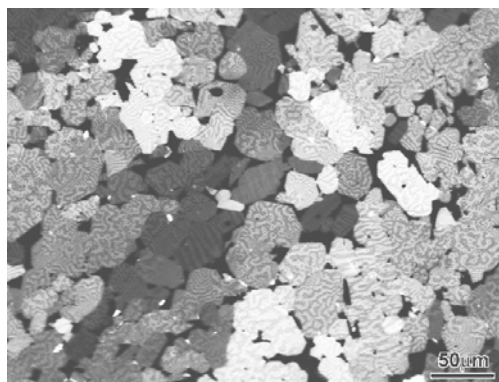


Figure 7 – Kerr effect image of the Pr₁₄Fe_{63.50}Co₁₆B₆Nb_{0.5} alloy.

CONCLUSIONS

It has been shown that niobium substitution in the rare earth-iron-boron-system led to a decrease in the Curie temperature. This diminution is quite noticeable when the niobium content is larger. Single substitution of Co and Nb led to the grain growth of the homogenized PrFeB-type alloy. Niobium acts as a grain refining only when cobalt is present in the Pr-based homogenized alloy. At the concentration of 0.1 at.% Nb this effect seem to be more evident. Grain refinement has been attributed to boride and Nb precipitates.

ACKNOWLEDGMENTS

The authors wish to thank FAPESP, IPT and IPEN-CNEN/SP for the financial support and infrastructure made available to carry out this investigation.

REFERENCES

- [1] JURCZYK, M.; CHISTJAKOV, O.D. Crystallographic and magnetic properties of $R_2(\text{Fe, Co, Nb})_{14}$ B-based systems (R= Pr, Pr-Dy). ***Journal of Magnetism and Magnetic Materials***. 78 (1989), 279.
- [2] BOLTICH, E.B.; OSWALD, E.; HUANG, M.Q.; HIROSAWA, S.; WALLACE, W.E.; BURZO, E. Magnetic characteristics of $R_2\text{Fe}_{14}\text{B}$ systems prepared with high purity rare earths (R= Ce, Pr, Dy, and Er). ***Journal of Applied Physics***. 57(1) (1985), 4106.
- [3] HUANG, M.Q.; BOLTICH, E.B.; WALLACE, W.E. Magnetic characteristics of $R_2(\text{Fe, Co})_{14}\text{B}$ systems (R= Y, Nd and Gd). ***Journal of Magnetism and Magnetic Materials***. 60 (1986), 270.
- [4] PEDZIWIATR, A.T.; JIANG, S.Y.; WALLACE, W.E. Structure and magnetism of the $\text{Pr}_2\text{Fe}_{14-x}\text{Co}_x\text{B}$ systems. ***Journal of Magnetism and Magnetic Materials***. 62 (1986), 29.
- [5] HERBST, J.F.; YELON W, B. Preferential site occupation and magnetic structure of $\text{Nd}_2(\text{Co}_x\text{Fe}_{1-x})_{14}$. ***Journal of Applied Physics***. 60(12) (1986), 4224.
- [6] FARIA, R.N.; DAVIES, B.E.; BROWN, D.N.; HARRIS, I.R. Microstructural and magnetic studies of cast and annealed Nd and PrFeCoBZr alloys and HDDR materials. ***Journal of Alloys and Compounds***. 296 (2000), 223.
- [7] BARBOSA, L. P. ***Estudo das propriedades e microestrutura de ímãs permanentes pelo processo de hidrogenação, desproporção, dessorção e recombinação (HDDR)***. Tese (Doutorado). IPEN/USP/SP São Paulo 2005. 134 p.
- [8] BARBOSA, L. P., TAKIISHI, H.; FARIA, R. N.; RODRIGUES, D.; JANASI, S. R. Curie temperature determination of $\text{Pr}_{14}\text{Fe}_{79,9-x}\text{Co}_x\text{B}_6\text{Nb}_{0,1}$ permanent magnet alloys, ***Material Science Forum*** (accept for publication)
- [9] PEDZIWIATR, A.T.; SANKAR, S.G.; WALLACE, W.E. The effect of Ga substitution on the magnetic properties of $\text{Nd}_2\text{Fe}_{14}\text{B}$, $\text{Pr}_2\text{Fe}_{14}\text{B}$ and PrCo_5 . ***Journal of Applied Physics***. 63 (8) (1988), 3710.

[10] FARIA, R.N.; YIN, J.X.; ABELL, J.S.; HARRIS, I.R. Microstructural and magnetic studies of Pr-Fe-B-Cu HD sintered magnets. ***Journal of Magnetism and Magnetic Materials*** 129 (1994), 263.

[11] ONELLY, J.C.S.; TSCHIPTSCHIN, A.P.; LANDGRAF, F.J.G. Influence of Co addition in the microstructure of NdFeB alloys. In Proceeding of the Eighth International Symposium on Magnetic Anisotropy and Coercivity in Rare-Earth Transition Metal Alloys, Birmingham, September, (1994), 261.

[12] BARBOSA, L.P., TAKIISHI, H.; FARIA, R. N.; The effect of cobalt on the microstructure of Pr-Fe-Co-B-Nb alloys and magnetic properties of HDDR magnets. ***Journal of Magnetism and Magnetic Materials***. 268 (2004), 132.