

THE EFFECT OF MILLING TIME UPON MICROSTRUCTURES OF Pr-Fe-B HD SINTERED MAGNETS PREPARED BY A LOW COST POWDER TECHNIQUE

E. P. Soares, E. A. Ferreira, E. A. Périgo, H. Takiishi, R. N. Faria

Av. Prof. Lineu Prestes, 2242 - CEP 05508-000; e-mail: epsoares@ipen.br

Instituto de Pesquisas Energéticas e Nucleares, IPEN-CNEN/SP, Brazil

ABSTRACT

Pr₁₇Fe₇₉B₄ and Pr₁₆Fe₇₆B₈ magnets have been produced using a combination of the hydrogen decrepitation (HD) process and a powder transfer technique. Sintered magnets have been prepared using HD powders ball milled from 9 to 36 hours. The effects of the milling stage upon microstructure have been investigated. In the Pr₁₇Fe₇₉B₄ magnets four phases have been identified: Pr₂Fe₁₄B (Φ), Pr rich, Pr₂Fe₁₇ and Laves phase (PrFe₂). In the Pr₁₆Fe₇₆B₈ magnets three phases have been identified: Pr₂Fe₁₄B (Φ), Pr rich and Pr_{1+ ϵ} Fe₄B₄ (η). Good magnetic properties have been achieved in the Pr₁₆Fe₇₆B₈ magnet produced using a fine powder milled for 18 hours ($B_r = 1.19$ T and $\mu_{0i}H_c = 1.44$ T). For the Pr₁₇Fe₇₉B₄ magnet a longer milling time has been necessary to improve the magnetic properties ($B_r = 1.14$ T and $\mu_{0i}H_c = 1.16$ T). In this case remanence and coercivity were slightly lower than that obtained in former due to the low boron content in the alloy (4 at.%).

Keywords: Pr-Fe-B magnets, Hydrogen decrepitation, Rare earth magnets.

INTRODUCTION

The influence of milling step on the magnetic properties and microstructures of rare earth-iron-boron-type magnets (RE = Nd and Pr) have been studied by various authors¹⁻³. Particle size after milling and grain size after sintering are very important interdependent factors for controlling the microstructure and, hence, the magnetic properties of the sintered magnets. Recently, a new powder transfer technique has been developed for production of such magnets in a laboratory scale^{4,5}. Nd and Pr-

based magnets were successfully produced using various milling times and this low cost technique. In this work the microstructures and mean grain size of the Pr-based HD magnets have been investigated.

EXPERIMENTAL PROCEDURE

Commercially available $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ alloys were processed in the as-cast state (ingot broken pieces). The processing conditions and magnetic properties of these HD magnets have been reported previously⁵. The microstructural and microanalysis characterization of the alloys and magnets were carried out using a scanning electron microscope fitted with energy dispersive X-ray analysis. Grain size measurements were carried out using optical microscope fitted with an image analyzer. Samples were etched with nital (3%) in order to reveal the grain boundaries for measurement of the mean grain size.

RESULTS AND DISCUSSION

The microstructures of the $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ as-cast alloys are shown in Fig. 1a and b, respectively. The $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ alloy is composed of the matrix phase $\text{Pr}_2\text{Fe}_{14}\text{B}$ (ϕ), praseodymium-rich phase and α -Fe (free-iron). The $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ alloy is also composed by same phases identified in the former with an extra boron-rich phase ($\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4$ or η). Various works reported these typical phases in sintered magnets⁶⁻¹². A comparison between these two microstructures shows that the alloy with high boron content has a somewhat more refined structure.

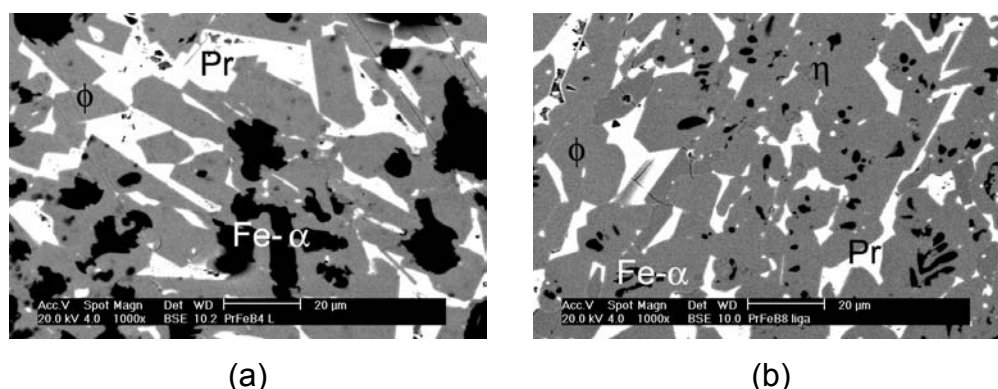


Fig. 1. Microstructures of as-cast alloys: a) $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and b) $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$; (1000x).

The chemical compositions of the phases determined by EDX on a SEM for as-cast alloys $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ are given in Table 1. The matrix phase $\text{Pr}_2\text{Fe}_{14}\text{B}$ (ϕ) and boron rich $\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4$ (η) were identified by Fe:Pr ratio¹³. Both phases, $\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4$ and $\alpha\text{-Fe}$, are detrimental to the magnetic properties of the sintered magnet. The magnetic properties of HD sintered magnets prepared from the $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ alloys are given in Tables 2 and 3, respectively.

Table 1 – Composition determined by EDX of phases present at as-cast alloys $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ and $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$.

Alloy	Phase	Chemical composition (at.%)	
		Pr	Fe
$\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$	$\text{Pr}_2\text{Fe}_{14}\text{B}$ (ϕ)	13.9±0.3	86.1±1.7
	Pr rich	94.4±1.8	5.6±0.1
	$\alpha\text{-Fe}$	1.2±0.03	98.8±2.0
$\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$	$\text{Pr}_2\text{Fe}_{14}\text{B}$ (ϕ)	13.4±0.3	86.6±1.7
	$\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4$ (η)	24.9±0.5	75.1±1.5
	Pr rich	83.3±1.6	12.5±0.3
	$\alpha\text{-Fe}$	1.1±0.03	98.9±2.0

Table 2 – Magnetic properties of $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ HD sintered magnets produced from the as-cast alloy using various milling times⁵.

Milling time (h)	B_r (T)	$\mu_0 iH_c$ (T)	$\mu_0 bH_c$ (T)	$(BH)_{\text{max}}$ (kJ/m^3)	SF	ρ (g/cm^3)
9	1.05	1.03	0.78	167	0.42	6.15
18	1.06	1.06	0.83	197	0.60	7.33
27	1.14	1.16	0.93	217	0.61	7.35
36	1.04	1.12	0.81	175	0.36	7.37

Table 3 – Magnetic properties of Pr₁₆Fe₇₆B₈ HD sintered magnets produced from the as-cast alloy using various milling times⁵.

Milling time (h)	B _r (T)	μ _{0i} H _c (T)	μ _{0b} H _c (T)	(BH) _{max.} (kJ/m ³)	SF	ρ (g/cm ³)
9	1.02	1.00	0.79	197	0.64	7.28
18	1.19	1.44	1.08	280	0.78	7.33
27	0.95	1.50	0.85	158	0.63	7.37
36	0.92	1.37	0.81	151	0.53	7.32

The microstructures of the HD sintered magnets prepared from as-cast alloys employing various milling times are shown in Figs. 2 (a-d and a'-d'). The phases found are identified in the micrographics. In the magnets prepared using the Pr₁₇Fe₇₉B₄ alloy were identified the matrix phase (ϕ), the Pr rich in the grain boundaries of the matrix phase, the phase Pr₂Fe₁₇ and the Laves Phase PrFe₂. The Pr₂Fe₁₇ phase is deleterious for magnetic properties because it causes reversal magnetization and diminution of the intrinsic coercivity in the sintered magnets. This phase is localized inside of the matrix phase and was not identified in the Pr₁₇Fe₇₉B₄ alloy (Fig. 1 a). This phase is present only in permanent magnets prepared using alloys with less than 5% at. B^{14,15,16}. Low boron content promotes the formation of the phase Pr₂Fe₁₇ and this inhibits the growing of the matrix phase¹⁴. The Laves phase, PrFe₂, is found in the grain boundary of matrix phase together with the Pr-rich phase.

In the HD sintered magnets prepared from alloy Pr₁₆Fe₇₆B₈ three phases were identified: the Pr₂Fe₁₄B matrix phase (ϕ), Pr-rich and B-rich phases (Pr_{1+ε}Fe₄B₄). The boron-rich phase is invariably found in magnets with B-content superior to 5% at. The chemical composition the phases determined by EDX in the HD sintered magnets prepared from the Pr₁₇Fe₇₉B₄ and Pr₁₆Fe₇₆B₈ alloys are given in Table 4 and 5. Boron cannot be analyzed by EDX and the phase were identified using Fe:Pr ratio¹³.

The microstructures revealing the grain boundaries of the HD sintered magnets prepared with Pr₁₇Fe₇₉B₄ and Pr₁₆Fe₇₆B₈ alloys is shown in Figure 3. Fig. 4 shows the mean grain size analyzed using an Image Analyzer.

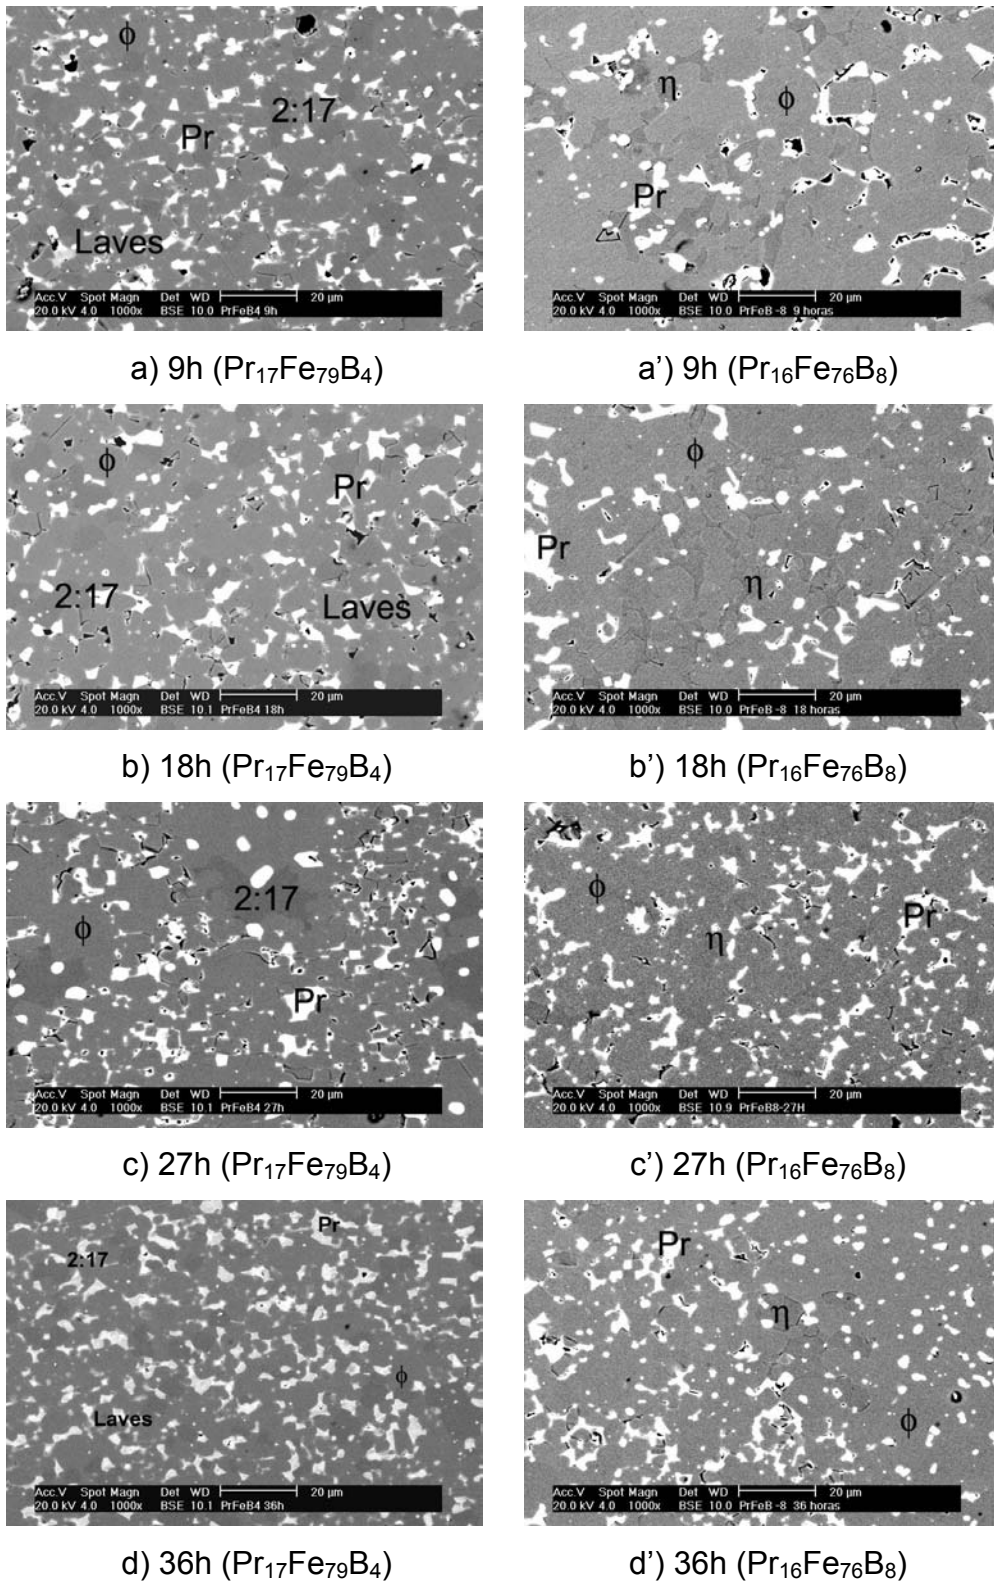


Fig. 2 – Micrographics of the $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ HD sintered magnets (a-d) and for the $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ HD magnets (a'-d'), milling time: 9, 18, 27 e 36 hours; (1000x).

Table 4. Chemical composition determined by EDX for the phases present on the $\text{Pr}_{17}\text{Fe}_{79}\text{B}_4$ magnets.

Milling time (h)	Phase	Chemical composition (at.%)	
		Pr	Fe
9	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	13.4±0.3	86.6±1.7
	$\text{Pr}_2\text{Fe}_{17}$	11.6±0.2	88.4±1.8
	Pr rich	89.8±1.8	10.2±0.2
	Laves	32.1±0.6	67.9±1.3
18	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	13.3±0.3	86.7±1.7
	$\text{Pr}_2\text{Fe}_{17}$	11.5±0.2	88.5±1.8
	Pr rich	89.0±1.8	11.0±0.2
	Laves	23.4±0.5	76.6±1.5
27	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	13.3±0.3	86.7±1.7
	$\text{Pr}_2\text{Fe}_{17}$	11.5±0.2	88.5±1.8
	Pr rich	89.7±1.8	10.3±0.2
	Laves	22.1±0.5	77.9±1.5
36	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	13.3±0.3	86.7±1.7
	$\text{Pr}_2\text{Fe}_{17}$	11.6±0.2	88.4±1.8
	Pr rich	89.9±1.8	10.1±0.2
	Laves	22.3±0.5	77.7±1.5

Table 5. Chemical composition determined by EDX for the phases present on the $\text{Pr}_{16}\text{Fe}_{76}\text{B}_8$ magnets.

Milling time (h)	Phase	Chemical composition (at.%)	
		Pr	Fe
9	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	14.4±0.3	85.6±1.7
	$\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4 (\eta)$	24.6±0.5	75.4±1.5
	Pr rich	88.1±1.7	11.9±0.2
18	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	14.2±0.3	85.8±1.7
	$\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4 (\eta)$	26.0±0.5	74.0±1.5
	Pr rich	87.8±1.7	12.2±0.3
27	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	14.7±0.3	85.3±1.7
	$\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4 (\eta)$	24.7±0.5	75.3±1.5
	Pr rich	88.0±1.7	12.0±0.2
36	$\text{Pr}_2\text{Fe}_{14}\text{B} (\phi)$	14.3±0.3	85.1±1.7
	$\text{Pr}_{1+\epsilon}\text{Fe}_4\text{B}_4 (\eta)$	23.6±0.5	76.4±1.5
	Pr rich	85.4±1.6	14.6±0.4

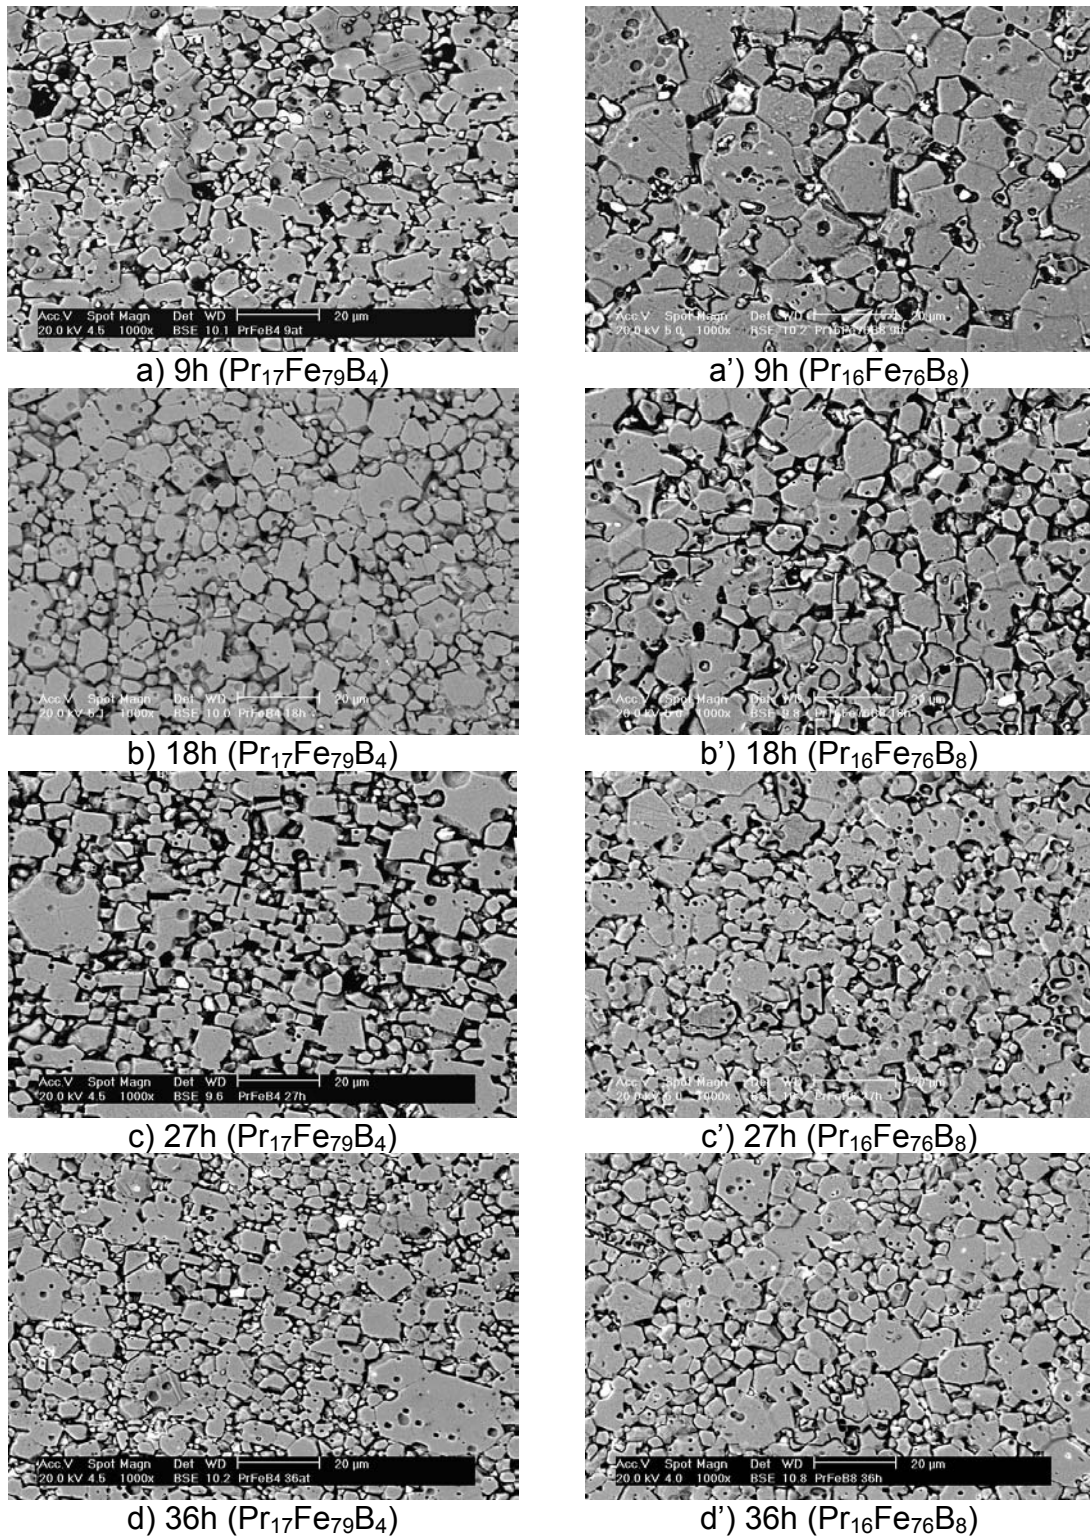


Fig. 3 – Micrographs showing a general view of the microstructures of the sintered magnets prepared using various milling times (1000x; etched with Nital).

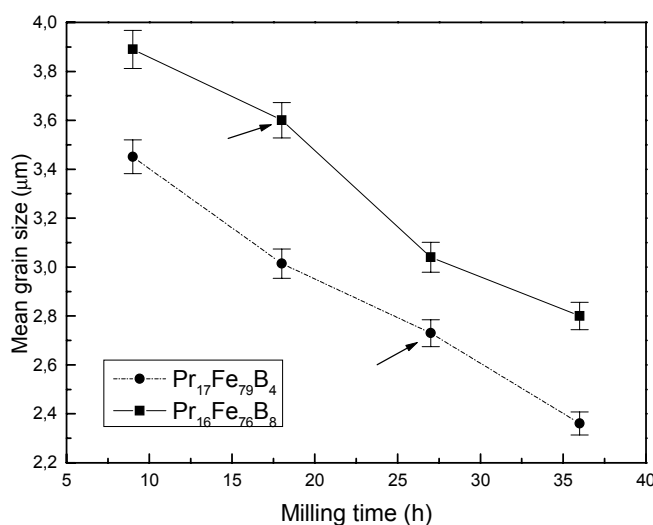


Fig. 4 – Mean grain size versus milling time for the HD sintered magnets prepared with the Pr₁₇Fe₇₉B₄ (---) and Pr₁₆Fe₇₆B₈ (—) alloys. The arrows indicate the magnets with best magnetic properties.

The mean grain size decrease with increasing milling time and the best magnetic properties were obtained in 27 and 18 hours for the magnets prepared from Pr₁₇Fe₇₉B₄ e Pr₁₆Fe₇₆B₈ alloys, respectively. In general the grain size is smaller for the sintered magnets prepared with Pr₁₇Fe₇₉B₄ alloy. This has been attributed to the presence of the Pr₂Fe₁₇ phase. It is believed that this phase inhibit the matrix phase growth during the sintering¹⁴. Prolonged milling times diminished the magnetic properties for magnets prepared with both alloys. This has been attributed previously to superficial oxidation and crystal structure defects^{2,17,18}.

CONCLUSIONS

It has been shown that the Pr₂Fe₁₇ phase causes a decrease in the mean grain size of the HD sintered magnets prepared with Pr₁₇Fe₇₉B₄ alloy (compared to that of magnets prepared with Pr₁₆Fe₇₆B₈ alloy). The presence of the Pr₂Fe₁₇ and PrFe₂ phases at Pr₁₇Fe₇₉B₄ magnets was more deleterious to the magnetic properties than the presence of the B-rich phases (Pr_{1+ε}Fe₄B₄) in the Pr₁₆Fe₇₆B₈ sintered magnets. Prolonged milling times were not beneficial to improve the magnetic properties of the sintered magnets prepared with both alloys.

ACKNOWLEDGMENTS

Many thanks are due to FAPESP and IPEN-CNEN/SP for supporting this investigation.

REFERENCES

1. NOH, T. H.; JEUNG, W. Y.; KANG, I. K.; SHIN, S. H.; LEE, J. J. Magnetic properties of Pr-Fe-B alloy powders prepared by mechanical grinding. *Journal of Applied Physics*, v. 70, n. 10, p. 6591-6593, 1991.
2. FARIA, R. N.; ABELL, J. S.; HARRIS, I. R. High coercivity sintered Pr-Fe-B-Cu magnets using the hydrogen decrepitation process. *Journal of Alloys and Compounds*, v. 177, p. 311-320, 1991.
3. FARIA, R. N.; WILLIAMS, A. J.; ABELL, J. S.; HARRIS, I. R. Magnetic properties of Pr-Fe-B sintered magnets produced from hydride powder and from partially and totally desorbed hydride powder. In: FOURTEENTH INTERNATIONAL WORKSHOP ON RARE-EARTHS MAGNETS AND THEIR APPLICATIONS, September 1-4, 1996, São Paulo, Brazil, p. 570-579.
4. TAKIISHI, H.; LIMA, L. F. C. P.; FARIA, R. N. The production of rare earth sintered magnets by a low cost powder technique. *Powder technology*, v. 127, p. 223-225, 2002.
5. SOARES, E. P.; PÉRIGO, E. A.; TAKIISHI, H.; MOTTA, C. C.; FARIA, R. N. A study of Pr-Fe-B magnets produced by a low-cost powder method and the hydrogen decrepitation process. *Materials Research*, vol. 8, n. 2, p.143-145, 2005.
6. TAKIISHI, H.; LIMA, L. F. C. P.; COSTA, I.; FARIA, R. N. The influence of process parameters and alloy structure on the magnetic properties of NdDyFeBNb HD sintered magnets. *Journal of Materials Processing Technology*, v. 152, p. 1-8, 2004.
7. SAGAWA, M.; FUJIMURA, S.; YAMAMOTO, H.; MATSUURA, Y.; HIRAGA, K. Permanent magnet materials based on the rare earth-iron-boron tetragonal compounds. *IEEE Transactions on Magnetics*, v. 20, n. 5, p. 1584-1589, 1984.
8. TOKUNAGA, M.; TOBISE, M.; MEGURO, N.; HARADA, H. Microstructure of R-Fe-B sintered magnets. *IEEE Transactions on Magnetics*, v. 22, n. 5, p. 904-906, 1986.
9. KOWN, H. W.; BOWEN, P.; HARRIS, I. R. A study of Pr-Fe-B-Cu permanent magnetic alloys. *Journal of Alloys and Compounds*, v. 182, p. 233-242, 1992.

10. MYCOCK, G. J.; FARIA R. N.; HARRIS, I. R. The microstructures and magnetic properties of some cast and annealed Pr-Fe-Cu-B alloy. ***Journal of Alloys and Compounds***, v. 201, p. 23-28, 1993.
11. MARCONDES, P. V. P. and FARIA, R. N. Microstructural studies on Pr-Fe-B-Cu magnets produced by upset forging of cast ingot. ***Materials Science and Engineering***, A272, p. 245-249, 1999.
12. CORFIELD, M. R.; WILLIAMS, A. J.; HARRIS, I. R. The effects of long term annealing at 1000°C for 24h on the microstructure and magnetic properties of Pr-Fe-B/Nd-Fe-B magnets based on Pr₁₆Fe₇₆B₈ and Nd₁₆Fe₇₆B₈. *Journal of Alloys and Compounds*, v. 296, p. 138-147, 2000.
13. FARIA, R. N.; TAKIISHI, H.; CASTRO, A. R. M.; LIMA, L. F. C. P.; COSTA, I. Chemical microanalysis of rare-earth-transition metal-boron alloys and magnets using scanning electron microscopy. ***Journal of Magnetism and Magnetic Materials***, v. 246, p. 351-359, 2002.
14. PAIK, C. R.; NAKAMURA, H.; OKADA, M.; HOMMA, M. Effects of B content on magnetic properties and microstructures in R(Ce, Pr, Nd)-Fe-B alloys. In: 9th INTERNATIONAL WORKSHOP ON RARE EARTH MAGNETS AND THEIR APPLICATIONS, Kyoto, Japan, 1989, p. 631-640.
15. FARIA, R. N.; YIN, X. J.; ABELL, J. S.; HARRIS, I. R. Microstructural and magnetic studies of Pr-Fe-B-Cu HD sintered magnets. ***Journal of Magnetism and Magnetic Materials***, v. 129, p. 263-270, 1994.
16. MARCONDES, P. V. P. and FARIA, R. N. Microstructural studies on Pr-Fe-B-Cu magnets produced by upset forging of cast ingot. ***Materials Science and Engineering***, A272, p. 245-249, 1999.
17. McGUINNESS, P. J.; DEVLIN, E.; ROZENDAAL, E.; ORMEROD, J. A.; HARRIS, I. R. A study of Nd-Fe-B magnets produced using a decrepitation and jet milling. ***Journal of Materials Science***, v. 24, p. 2541-2548, 1989.
18. ORMEROD, J. Powder metallurgy of rare earth permanent magnets. ***The International Journal of Powder Metallurgy***, v. 25, n. 3, p. 197-205, 1989.